

SENENICH WOOD PROPELLER CO., INC.

AREA CODE 813
PHONE - 752-3711
FAX - 752-2818



2008 WOOD COURT
PLANT CITY, FL USA
33563

See us on the Web @ www.sensenich.com


SUPPLEMENTAL AIRWORTHINESS INSTRUCTIONS FOR BONDED METAL EROSION SHIELD

The following practices will assist you in determining airworthiness of the bonded metal erosion shield(ES) on your Sensenich Propeller. The information is provided as a supplement to model specific installation instructions for propellers with bonded metal erosion shields.

EROSION SHIELD DAMAGE LIMITATIONS OF SAFE OPERATION

If your erosion shield begins to show any of the following damage, it should be removed from service and inspected by a rated repair station before next operation:

- 1) Any dent or erosion that punctures the erosion shield or exposes composite or core material underneath.
- 2) Any dent or erosion greater than 1/16" deep.
- 3) Circular or pointed dents greater than ¼ x ¼".
- 4) Any cracks in the metal erosion shield.
- 5) Any debond greater than .39 in².
- 6) Any debond greater than 1" spanwise length.
- 7) Any debond greater than 30% of the erosion shield width.
- 8) Debonds within 5 inches of each other.
- 9) More than 5 debonds of any size.

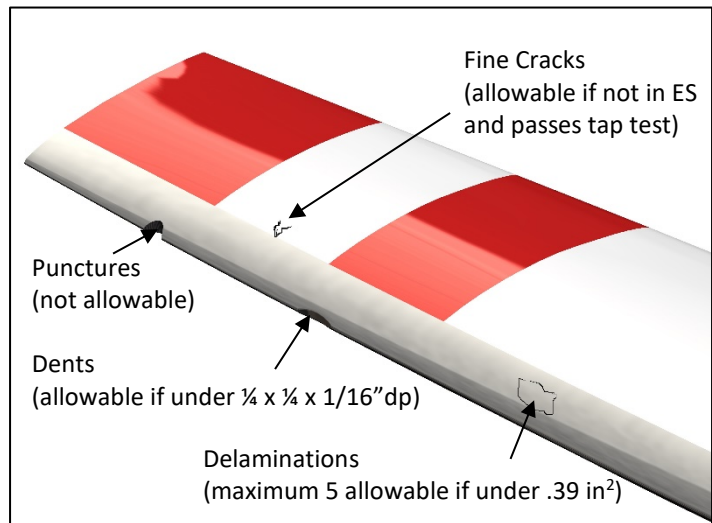


VISUAL INSPECTION

Visually inspect the propeller blade. Check for impact damage along the leading edge. Verify that any damage or erosion falls under the limits set for erosion shield damage. Check for cracks in the erosion shield or in the blade area around the erosion shield. Cracks occurring in the metal require immediate erosion shield replacement. Fine cracks in the finish of the propeller blade at the inboard area of the erosion shield or running along the edge of the erosion shield are not dangerous and allowable if they pass a coin tap test.

COIN TAP TEST

Debonds and delaminations within the laminate or under the erosion must be inspected for using a coin tap test. Using a coin or washer similar in size to a quarter, tap the entire surface of the erosion shield and blade. Solid laminate will produce a high pitch note. Debonded or delaminated areas will have a hollow, dead response.

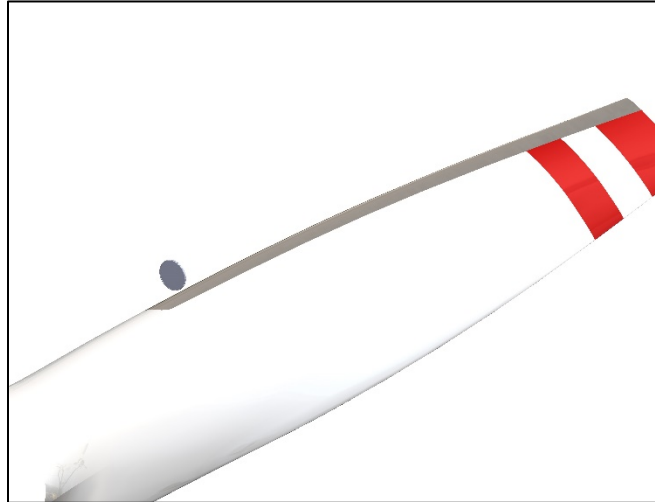

FIELD REPAIR GUIDELINES

Any damage to the propeller that punctures the outer erosion shield or laminate requires that the propeller be serviced by a rated propeller repair station. Damage that does not puncture the outer surface and falls within the safe operating limits may be repaired in the field if desired. Use the following steps for minor repairs:

- 1) Sand and clean damaged area for proper adhesion. Take care not to sand through or damage erosion shield or composite shell.
- 2) Fill in area with epoxy resin to original blade shape.
- 3) Once cured, sand resin to blend to original blade contour.
- 4) Refinish area as needed. Ensure no moisture can penetrate finish.
- 5) Inspect this area for further cracks or wear during pre-flight inspections.